

## **Physical and SPF Value Stability Studies Avocado Oil Nano-emulgel with Carbopol 980 as A Gel Base**

**Ayu Shabrina<sup>1\*</sup>, Diva Ma'arif Pangestu<sup>2</sup>, Siska Amaliyah<sup>2</sup>, Malinda Prihantini<sup>1</sup>, Junvidya Heroweti<sup>3</sup> and Listyana Dewi Prastiwi<sup>4</sup>**

<sup>1</sup>Department of Pharmaceutics and Pharmaceutical Technology, Faculty of Pharmacy, Universitas Wahid Hasyim, Semarang, Indonesia

<sup>2</sup>Faculty of Pharmacy, Universitas Wahid Hasyim, Semarang, Indonesia

<sup>3</sup>Department of Pharmacology and Clinical Pharmacy, Faculty of Pharmacy, Universitas Wahid Hasyim, Semarang, Indonesia

<sup>4</sup>Faculty of Pharmacy, Universitas Muhammadiyah Kalimantan Timur, Samarinda, Indonesia

\*Corresponding author: [shabrina@unwahas.ac.id](mailto:shabrina@unwahas.ac.id)

**Received:** March 2, 2025; **Accepted:** May 27, 2025; **Published:** June 22, 2025

### **Abstract**

Avocado oil (AVO) is a natural source of many unsaturated fatty acids that can help protect the skin from harmful UV radiation. The high content of unsaturated fatty acids in avocado oil can affect product stability. One way to overcome the stability of avocado oil for topical preparation is by formulating it into a gel base using Carbopol 980. The purpose of this study was to determine the physical stability and SPF value of avocado oil nano-emulgel (NE) with variations of Carbopol 980 as a gel base for 28 days of storage. AVONE was made with 5% AVO and Carbopol 980 base variation of 0.5% (NE1), 1.0% (NE2;), and 1.5% (NE3.) AVONE was stored in a climatic chamber at  $30^{\circ} \pm 2^{\circ}\text{C}$  with RH  $65\% \pm 5\%$ . The samples were tested for physical and SPF values before storage on days 7, 14, 21, and 28. The data obtained were analyzed statistically using one-way Anova. The AVONE on organoleptic parameters were stable; the resulting colour is broken-white with a distinctive oil aroma and thick and homogeneous texture. The pH value ranged from  $6.21 \pm 0.02$  -  $7.21 \pm 0.02$ , with all formulas stable during storage. The viscosity value ranged from  $13.28 \pm 0.23$  -  $47.22 \pm 0.89$  dPa.s; the viscosity of NE3 was stable during storage. Adhesion and spreadability showed good ability to adhere to the skin. The SPF values ranged from  $8.95 \pm 0.43$  -  $22.41 \pm 0.21$ , and NE3 was stable during storage. Avocado oil nano-emulgel with Carbopol 980 concentration of 1.5% was stable during storage.

**Keywords:** Avocado oil; Carbopol; Emulgel; Nano-emulgel; Stability

### **1. INTRODUCTION**

Avocado oil is a natural source of many unsaturated fatty acids such as oleic, linoleic, and palmitic acids, which can help protect the skin from harmful UV radiation (Suradnyana et al., 2023). Avocado oil contains unsaturated fatty acids totalling 85.72%(Li et al., 2019). The higher content of unsaturated fatty acids in avocado oil make it easy to oxidize and lead to be spoiled oil (Hermanto et al., 2010).

Avocado oil can increase collagen synthesis, reduce the number of inflammatory cells, accelerate coagulation, and accelerate epithelial regeneration (Ebad Sichani et al., 2021). Avocado oil is a rich source of oleic acid (unsaturated fatty acid), which can increase collagen synthesis. However, the content of unsaturated fatty acids in avocado oil can cause oxidation reactions due to its poor stability (A. P. De Oliveira et al., 2013). Avocado oil has a comedogenic rating of 3 when used directly on the skin (Ghani et al., 2021). Avocado oil may clog pores in some skin types, potentially causing acne or skin issues in sensitive individuals. One way to overcome the instability of avocado oil is to formulate it into nano-emulgel (Eid et al., 2013; Scomoroscenco et al., 2021)

Previous research has formulated avocado oil in several dosage forms, such as nanoemulsion (NS), emulgel and nano-emulgel (NE) with Carbopol 940 (Dewi et al., 2024; Eid et al., 2013; Shabrina, 2024). Avocado oil NS showed good stability and globule size. The avocado oil SPF value and MED (Minimum Erythematous Dose) of outcomes are inferior to NS, potentially due to the gel base's effect. Consequently, it is essential to investigate the physical stability and SPF value of avocado oil formulated as a nano-emulgel with carbopol 980 to ensure product stability and efficacy. Nano-emulgel using Carbopol 980 offers advantages over cream formulations, including enhanced stability of the emulsion system, which is augmented by the increased viscosity of the aqueous phase due to the presence of a gelling agent. This configuration facilitates the delivery of both hydrophilic and hydrophobic compounds, as the nano-emulgel comprises a biphasic oil and water system (Priani et al., 2020). Another advantage of the nano-emulgel form is the presence of an oil phase component in the emulsion system as a suitable carrier for hydrophobic active substances such as avocado oil, which is difficult if formulated into a form that contains a lot of water, such as a gel (Hardenia et al., 2014). Nano-emulgel preparations are also known to adhere better than cream preparations, thereby increasing comfort and effectiveness of use (Sreevidya, 2019). Several polymer bases, including Carbopol 980, can be utilized to produce nano-emulgel.

Carbopol 980 is utilized as a basis owing to its advantages, including the transparent physical appearance of the nano-emulgel, compatibility, stability, and suitable viscosity (Nabillah et al., 2022). Carbopol 980 is recognized for providing a stable formulation at room temperature and during accelerated storage conditions (Shelke & Kulkarni, 2019). Carbopol is a base due to its excellent stability, absorption, spreadability, and non-sticky properties, making it suitable for sunscreen formulations (Ikhtiyarini & Sari, 2022). Carbopol 980, used as a gelling agent with a concentration of 0.5%, produces an ideal preparation. Carbopol 980 in nano-emulgel preparations produces stable preparations for 3 months at room temperature and accelerated storage conditions (Shelke & Kulkarni, 2019). However, despite these known advantages, there is a lack of research specifically evaluating how variations in Carbopol 980 concentration affect the physical stability and SPF value of nano-emulates incorporating avocado oil as the active component. It is necessary to investigate the impact of different base concentrations on the overall performance of the formulation. Based on the above background, it is necessary to conduct research related to the physical and SPF value stability of avocado oil

nanoemulsion in the form of nano-emulgel preparations with variations in Carbopol 980 base. This base type prevents phase separation and ensures uniform dispersion of UV-filtering actives critical for consistent SPF performance.

## 2. MATERIAL AND METHODS

### 2.1. Materials

The material used in this study was avocado oil (cosmetic grade) obtained from PT Daarjeling Aroma, Bandung, with a certificate of analysis. The carrier materials were Tween 80, Span 80, Sorbitol, Paraffin Liquid, TEA, methyl paraben, propyl paraben, and Carbopol 980 obtained from PT Multi Kimia Raya Semarang with cosmetic grade. DMSO and distilled water were obtained from PT Multi Kimia Raya Semarang with analytical grade.

The tools used in this study are a set of climatic chambers (Taisite HWS-70BX®), a viscometer (Rheosys Merlin II®) with type of cone and plate, a set of adhesion test equipment, a set of spreadability test equipment, and UV-Vis spectrophotometer (Shimadzu UV-1800®).

### 2.2. Methods

The preparations of nano-emulgel began with nanoemulsion production (Table 1). Tween 80 and PEG 400 were heated at 35°C in a different beaker glass. Tween 80 and PEG 400 were mixed using a magnetic stirrer at 700 rpm. The avocado oil was then added dropwise into the mixture, stirred at 1200 rpm until homogenous, and showed a clear and transparent nanoemulsion. The product was tested for particle size, polydispersity index and zeta potential to ensure that the preparation falls into nanoemulsion category.

**Table 1.** Formula of avocado oil nanoemulsion with carbopol 980 variations.

| Materials       | Concentration (%b/v) |           |       |
|-----------------|----------------------|-----------|-------|
|                 | NE1                  | NE2       | NE3   |
| Avocado oil     |                      | 7.5       |       |
| Tween 80        |                      | 30        |       |
| PEG 400         |                      | 40        |       |
| Carbopol 980    | 0.50                 | 1.00      | 1.50  |
| Tween 80        | 12.50                | 12.50     | 12.50 |
| Span 80         | 2.50                 | 2.50      | 2.50  |
| Sorbitol        | 1.00                 | 1.00      | 1.00  |
| Paraffin Liquid | 1.25                 | 1.25      | 1.25  |
| Methyl parabene | 0.18                 | 0.18      | 0.18  |
| Propyl paraben  | 0.02                 | 0.02      | 0.02  |
| Triethanolamine | 0.80                 | 0.80      | 0.80  |
| Distilled water |                      | Up to 100 |       |

The preparation of nano-emulgel begins with weighing each ingredient according to the formula in Table 1. The gel phase (Carbopol 980) was made by dispersing the polymer base (Carbopol 980) into hot water at 80°C and stirring in a mortar until a thick gel mass was formed. The emulsion phase was then made consisting of an aqueous phase (methylparaben, and tween 80) and an oil phase (propylparaben, liquid paraffin, and span 80), each phase of which was

first homogenized in a waterbath that had been adjusted to a temperature of 70°C. The oil phase was added to the water phase in a glass beaker. The mixture was stirred using a magnetic stirrer set at 40°C and a speed of 500 rpm; then distilled water and sorbitol were added and stirred until homogeneous, after which avocado oil was added little by little with stirring until homogeneous. The homogeneous emulsion phase is mixed with the gel base (Carbopol 980) that has been formed. Each formula was produced for three replications.

Avocado oil nano-emulgel was stored in a climatic chamber at  $30^{\circ} \pm 2^{\circ}\text{C}$  with RH 65%  $\pm$  5%. Samples were tested before storage and on days 7, 14, 21, and 28 (Nabillah et al., 2022)(FDA, 2013). The parameters tested were:

#### 2.2.1. Organoleptical test

Organoleptic testing is done by direct observation using the five senses, including colour, odour and consistency of the nano-emulgel made (Depkes RI, 1995).

#### 2.2.2. Homogeneity test

A nano-emulgel preparation of 0.1 g was applied to a transparent glass plate and observed for homogeneity. The test preparation must show a homogeneous arrangement, indicated by the absence of coarse grains on the glass object (Voigt, 1984).

#### 2.2.3. pH test

The pH measurement was carried out using a pH meter at room temperature. Before use, the pH meter electrode is washed, rinsed with distilled water, and dried. The tool is calibrated using a standard buffer solution of pH four and pH 7 (BPOM RI, 1995). The pH test is also carried out to determine if the pH of the nano-emulgel preparation meets the requirements according to SNI 16-3499-1996. A good pH for the skin is 4.5-8 (Chandra & Rahman, 2022).

#### 2.2.4. Viscosity test

The viscosity test was conducted with a Rheosys Merlin II-type cone and plate viscometer. A sample of 0.5 g was put into the plate, and then the cone was positioned to start the measurement. Viscosity and flow curves are generated automatically with the Rheosys Micra application (Nabillah et al., 2022).

#### 2.2.5. Adhesion test

The adhesion test is carried out by weighing the preparation as much as 0.25 grams placed on a glass object that has been determined in the area than another glass object is placed above. The glass object was then mounted on the test device, given a load of 1 kg for 5 minutes, and then released with a load weighing 80 grams. The time is recorded until the two glass objects are released (Allen, 1998).

#### 2.2.6. Spreadability test

A total of 0.5 grams of nano-emulgel preparation was placed in the centre of a transparent glass covered with graph paper underneath, then covered with another transparent glass on top,

given a load (50 g, 100 g, 150 g, 200g and 250g) and allowed to stand for 1 minute, measuring the diameter of the nano-emulgel spread area released (Voigt, 1984).

### 2.2.7. SPF value test

Determination of SPF value was done using a UV-Vis spectrophotometer by weighing 1 gram of avocado oil nano-emulgel, then put into a 10 ml volumetric flask and dissolved with DMSO as much as 5 ml. The solution was vortexed until completely dissolved. The solution that has been obtained is measured with a UV-Vis spectrophotometer at a wavelength of 290-320 nm using DMSO as a blank; then the absorbance value is recorded at every 5 nm interval. The recorded absorbance value were used to calculated the Sun Protection Factor (SPF) using the Mansur method (Mansur et al., 1986):

$$SPF = CF \times \sum_{290}^{320} EE(\lambda) \times I(\lambda) \times Abs(\lambda)$$


**Equation 1.** Calculation of Sun Protection Faactor (SPF) using the Mansur method (Mansur et al., 1986). *Description:* CF = correction factor, Abs ( $\lambda$ ) = absorption of sunscreen product,  $\sum_{290}^{320} EE(\lambda)$  = erythemal effect spectrum, I ( $\lambda$ ) = intensity of light spectrum.

### 2.3. Data analysis

Organoleptic and homogeneity test data were described descriptively, while pH, viscosity, adhesion, spreadability, and SPF values were analyzed statistically using one-way Anova to detect any physical changes in all formulas during 28 days of storage. Nano-emulgel is concluded as a stable product if no significant changes or significance values were  $> 0.05$ .

## 3. RESULTS AND DISCUSSION

The result of the nanoemulsion of avocado oil can be seen in Figure 1 and Table 2. The product was categorized as a nanoemulsion according to its particle size.

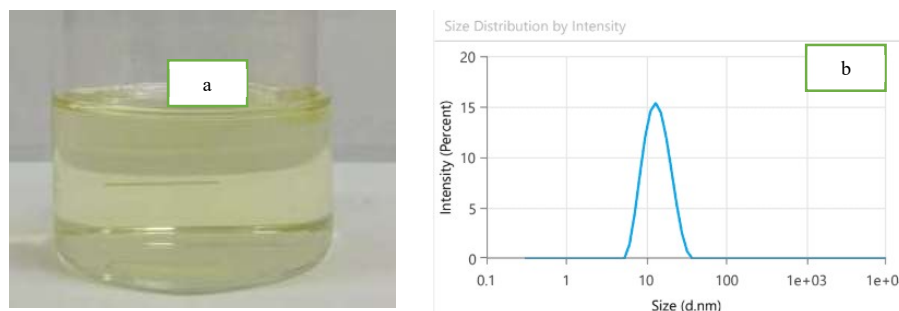

**Figure 1.** The result of the organoleptic test (a) and particle size (b) of avocado oil nanoemulsion.

Based on the result above, it can be concluded that the preparation was categorized as a nanoemulsion. The result of the particle size was below 100 nm, and the polydispersity index was below 0.5, showing that the nanoemulsion had a homogenous globule size (Widyastuti & Saryanti, 2023). The zeta potential was below 30 mV, indicating that the nanoemulsion had a good stability (Mardiyanto et al., 2024). Tween 80 with PEG 400 can create transparent and


stable nanoemulsions close to a micellar system (Artanti et al., 2021). Tween 80 is a hydrophilic surfactant that effectively decreases surface tension in nanoemulsion formulations (Suryani et al., 2020).

**Table 2.** The results of the physical test of avocado oil nanoemulsion and nano-emulgel. *Description:* NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980. Data displayed  $n = 3 \pm SD$ . \*Significantly different with nanoemulsion.

| Parameters           | Result                       |                                |                     |                     |
|----------------------|------------------------------|--------------------------------|---------------------|---------------------|
|                      | Nanoemulsion                 | Nano-emulgel                   |                     |                     |
|                      |                              | NE1                            | NE2                 | NE3                 |
| Physical appearance  | Clear and transparent liquid | Broken white with soft texture |                     |                     |
| Particle size (nm)   | $12.74 \pm 0.24$             | $320.72 \pm 1.22^*$            | $323.00 \pm 1.87^*$ | $322.00 \pm 0.92^*$ |
| Polydispersity index | $0.1415 \pm 0.02$            | $0.4318 \pm 0.04^*$            | $0.4325 \pm 0.07^*$ | $0.4320 \pm 0.05^*$ |
| Zeta potential (mV)  | $22.5 \pm 1.15$              | $-28.1 \pm 1.08^*$             | $-29.3 \pm 0.81^*$  | $-28.7 \pm 1.02^*$  |

The physical test results of NE1, NE2 and NE3 were significantly different with nanoemulsion ( $p = 0.001$ ), attributed to the aggregation of globules with the bases and other solvents in the emulgel. Carbopol could experience entrapment within the nanoemulsion system, increasing particle size relative to the nanoemulsion (Abdullah et al., 2023). Particle aggregation within the system can affect various parameters, including the polydispersity index and zeta potential (Al-Awady et al., 2017). The PDI data indicated that the nanoemulsion was monodisperse. This monodisperse system was also demonstrated in nano-emulgel. Prior studies indicated that nanoemulsions incorporated into hydrogels yield a polydispersity index of less than 0.5 and maintain stability for up to 90 days of storage (Alhasso et al., 2023). The zeta potential in all nanoemulgel formulations exhibited negative values, influenced by the carboxylate group of carbopol. Carboxylic groups can engage in electrostatic interactions when avocado oil droplets are integrated into the base, resulting in a stable colloidal structure (Alhasso et al., 2023). This result was in line with Shabrina et al. (2024) that nanoemulsion dispersed in carbopol as a gel base might experience changes such as zeta potential and globule size.


The results of the organoleptic test of avocado oil nano-emulgel preparations for NE1, NE2 and NE3 can be seen in Figure 2.

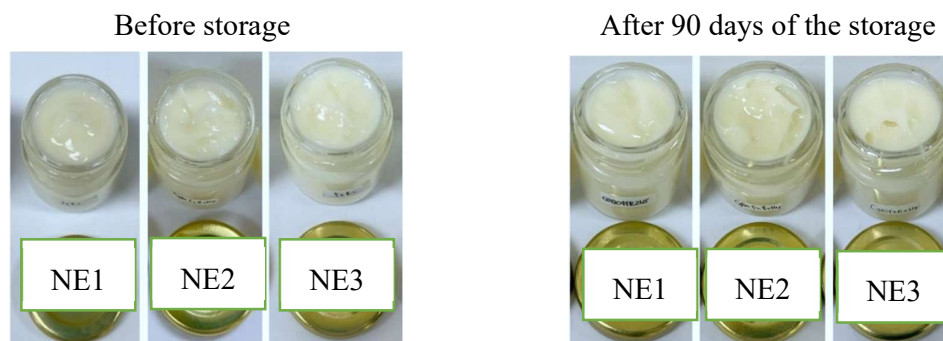

**Figure 2.** The result of the organoleptic test of avocado oil nano-emulgel with Carbopol 980 variations (NE1: 0,50%; NE2: 1,00%; NE3: 1,50%)

The results of organoleptic testing of avocado oil NE did not show any colour changes during 28 days of storage. The texture of the preparation in NE1 was slightly thick, while NE2 and NE3 had a thicker texture. The difference in texture of the three formulas was due to the different concentrations of Carbopol 980 base used in each formula. According to research by Nabillah et al. (2022), the greater the concentration of gelling agent used, the thicker the preparation's texture will be. After 28 days of storage, the three formulas became thinner in texture. This is because gel preparations might experience a syneresis. This event was caused by the release of water from the preparation, where the preparation shrinks so that it tends to squeeze water out of the preparation (Kuncari et al., 2014).

The homogeneity test results of avocado oil nano-emulgel preparations for NE1, NE2 and NE3 can be seen in Figure 3.

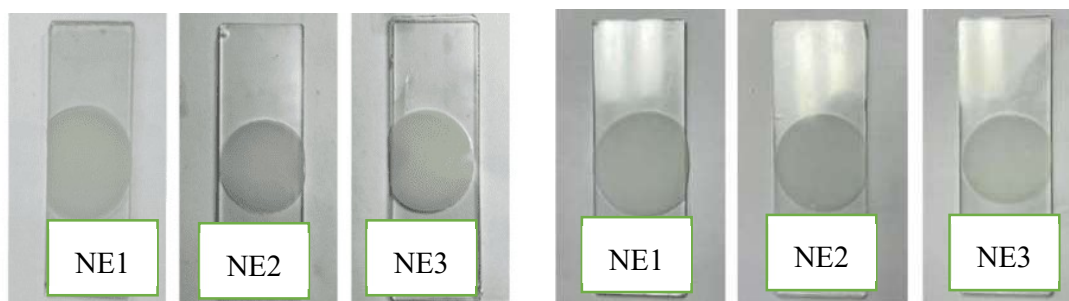

**Figure 3.** The result of Avocado oil nano-emulgel homogeneity test results before storage (a) and after the storage (b) with Carbopol 980 variations (NE1: 0,50%; NE2: 1,00%; NE3: 1,50%).

As shown in the picture above, NE1, NE2 and NE3 avocado oil nano-emulgel obtained homogeneous results for 28 days of storage. All formulas showed the absence of coarse grains or unmixed particles. The preparation exhibited inhomogeneity, as evidenced by coarse grains on the glass object (Voigt, 1984). The results of the homogeneity test obtained are in line with the research conducted by Nabillah et al. (2022), showing that the different concentrations of Carbopol 980 do not affect the homogeneity of the preparation.

The pH test results of avocado oil nano-emulgel preparations for NE1, NE2 and NE3 can be seen in Table 3.

The pH test results show that NE1 has a higher pH than NE2 and NE3. This indicates that increasing the concentration of Carbopol 980 can affect the pH of the nano-emulgel preparation. The greater the concentration of Carbopol 980 used, the lower the pH will be. avocado oil nano-emulgel pH in NE1, NE2 and NE3 obtained results between  $6.21 \pm 0.02$  -  $7.21 \pm 0.02$ . The pH value obtained is based on the range of pH requirements (SNI) for topical preparations, namely 4.5-8.

Based on the statistical analysis, the results did not show any significant difference in pH ( $p > 0.05$ ) in the three formulas, which means that there is no significant difference in the pH

value of avocado oil nano-emulgel preparations during the storage cycle, so it can be said that all formula is stable for 28 days of storage.

**Table 3.** The result of pH stability of avocado oil nano-emulgel with Carbopol 980 as a gel base. Description: *NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980, Data displayed  $n = 3 \pm SD$ .*

| Day            | pH        |           |           |
|----------------|-----------|-----------|-----------|
|                | NE1       | NE2       | NE3       |
| Before storage | 7.21±0.02 | 6.87±0.01 | 6.21±0.02 |
| 7              | 7.20±0.02 | 6.89±0.01 | 6.24±0.02 |
| 14             | 7.21±0.02 | 6.87±0.01 | 6.24±0.04 |
| 21             | 7.20±0.02 | 6.86±0.03 | 6.23±0.02 |
| 28             | 7.21±0.02 | 6.86±0.03 | 6.22±0.01 |
| p value        | 0.543     | 0.671     | 0.774     |


The viscosity test results of avocado oil nano-emulgel preparations for NE1, NE2 and NE3 (Table 4). The viscosity results showed changes during 28 days of storage in NE1, NE2 and NE3, but the changes in the three formulas are still within the range that meets the requirements for good nano-emulgel viscosity values, namely 3-300 dPa.s (Yuliandri et al., 2021). Based on the results of the viscosity values obtained showed that NE3 has a higher viscosity value than NE1 and NE2, and this is in line with previous research conducted by Nabillah et al. (2022), which shows that the higher concentration of Carbopol 980, the viscosity value of the preparation obtained increases. The increasing viscosity indicates a thicker preparation (Suhesti et al., 2022).

**Table 4.** The result of the viscosity test of avocado oil nano-emulgel with carbopol 980 as a gel base. Description: *NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980, Data displayed  $n = 3 \pm SD$ .*

| Day            | Viscosity (dPa.s) |            |            |
|----------------|-------------------|------------|------------|
|                | NE1               | NE2        | NE3        |
| Before storage | 16.88±0.08        | 43.16±0.07 | 45.33±0.66 |
| 7              | 15.61±0.22        | 40.65±0.25 | 46.42±0.91 |
| 14             | 15.48±0.15        | 39.32±0.22 | 46.38±0.82 |
| 21             | 14.31±0.25        | 38.35±0.41 | 47.30±0.78 |
| 28             | 13.28±0.23        | 37.45±0.28 | 47.22±0.89 |
| p value        | 0.001             | 0.024      | 0.512      |

Based on the statistical analysis, the viscosity value of NE3 did not show any significant difference ( $p > 0.05$ ), meaning there was no significant difference in the viscosity value of avocado oil nano-emulgel preparations during storage. In NE1 and NE2, there were significant changes ( $p < 0.05$ ) in the viscosity values of avocado oil nano-emulgel preparations during storage. Both NE1 and NE2 experienced a decrease in viscosity during storage. According to

research by Rismawati et al. (2020), this decrease in viscosity can occur due to the longer temperature and storage time. This is because the nano-emulgel experiences syneresis. Syneresis occurs due to the matrix structure or gel fibres that persist in solidifying, ultimately leading to the expulsion of water and enabling the liquid to migrate to the surface (Rao et al.,

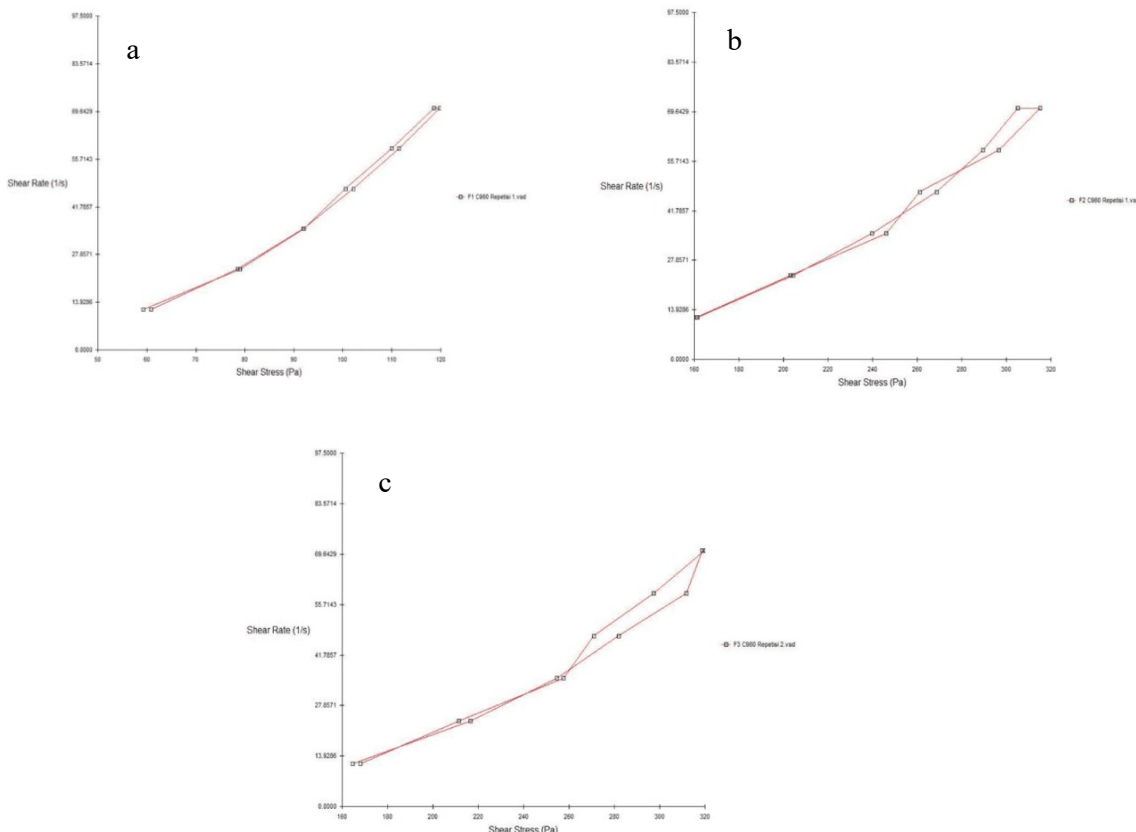


2023; Zalivskaya et al., 2021). This might be caused by the container system (Rao et al., 2023). The rheogram of avocado oil NE can be seen in Figure 4 and Figure 5.

**Figure 4.** Rheogram of avocado oil nano-emulgel with carbopol 980 as a gel base before storage of (a) NE1 (0,50%), (b) NE2 (1,00%), and (c) NE3 (1,50%).

The rheogram results show that nano-emulgel NE1, NE2 and NE3 rheology were categorized as pseudoplastic. Pseudoplastic is characterized by a slightly curved upward graph shape (Patricia & Yuliani, 2015). Pseudoplastic flow is characterized by a flow curve that intersects the origin (0,0), in contrast to plastic flow, indicating that pseudoplastic flow lacks a yield value. The viscosity of pseudoplastic substances decreases with increasing rate of shear. This occurs in long-chain molecules such as polymers. The pseudoplastic system is also called a dilute shear system because the viscosity decreases by increasing the shear stress (Kuncari et al., 2014). The rheology profile of all formulas did not show any changes. The rheology of Carbopol 980 is not affected by temperature and storage duration but by the cross-linker used during formulation (Islam et al., 2004). This type of rheology has advantages, such as increasing

viscosity after application when the shear is removed, helping the product stay in place and not drip off.

The pseudoplastic nature contributes to a non-dripping, non-sticky texture at rest and a smooth, pleasant feel during application—essential for user satisfaction with topical products like sunscreens. Pseudoplastic gels decrease viscosity under shear stress, such as during application, making them easier to spread on the skin or other surfaces. This behaviour ensures good adherence and uniform coverage, crucial for topical formulations (Jo et al., 2021). Gel with pseudoplastic rheology can withstand mechanical stresses during processing, such as pumping or extrusion, and application without breaking down or separating, contributing to long-term stability (Dantas et al., 2016).

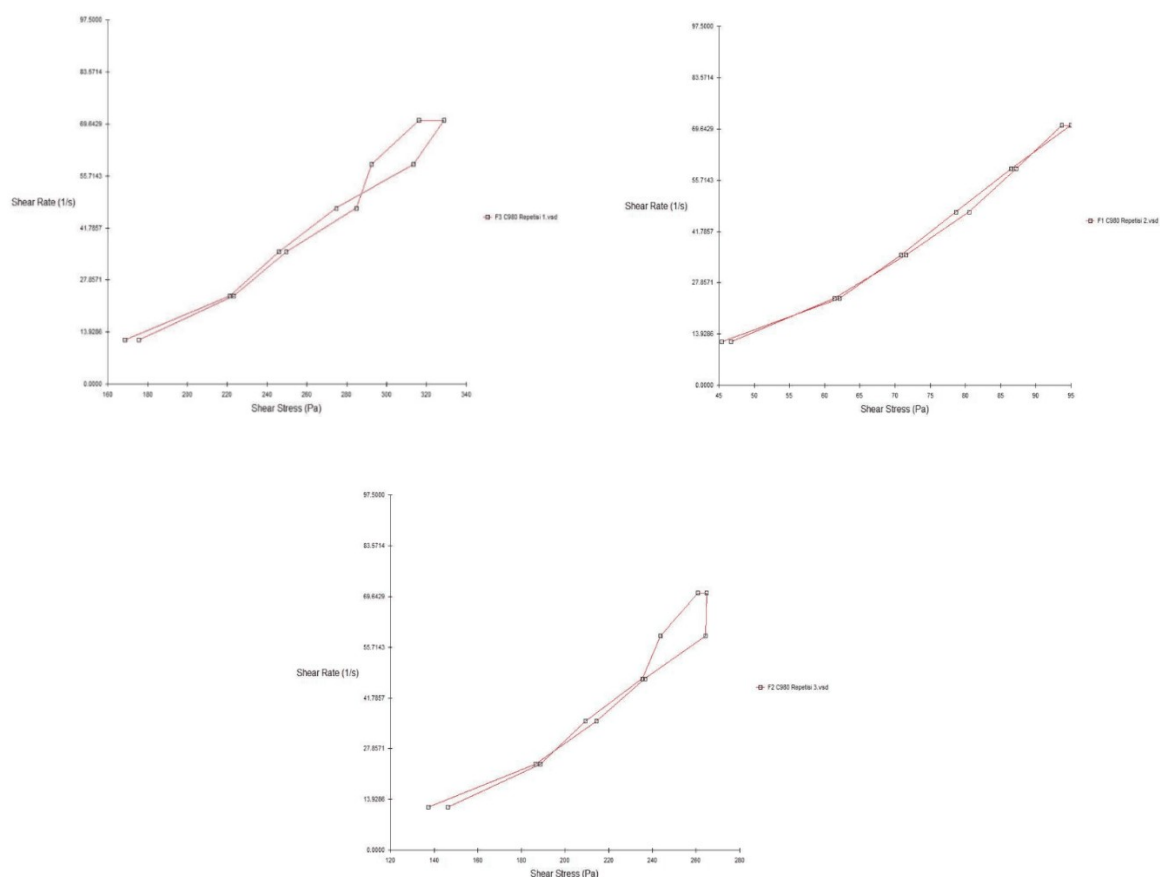

**Figure 5.** Rheogram of avocado oil nano-emulgel with carbopol 980 as a gel base after storage of (a) NE1 (0,50%), (b) NE2 (1,00%), and (c) NE3 (1,50%).

The results of the avocado oil nano-emulgel preparation adhesion test for NE1, NE2 and NE3 (Table 5). The results of the avocado oil nano-emulgel adhesion test showed that NE3 had a longer adhesion time than NE1 and NE2, but the adhesion of all formulas still met the requirements for good topical preparation adhesion, which is not less than 4 seconds. The results of the avocado oil nano-emulgel adhesion test show that the higher the concentration of

Carbopol 980, the more viscosity of the resulting preparation will increase so that the adhesion time will be longer (Numberi, 2020).

Based on the results of statistical analysis, the adhesion value of avocado oil nano-emulgel preparations shows significant results ( $p > 0.05$ ) in NE3, which means that there is no significant difference in the adhesion value of avocado oil nano-emulgel preparations during the storage cycle, so it can be said that NE3 is stable for 28 days of storage. In NE1 and NE2, the significance results ( $p < 0.05$ ) mean that there are significant differences in the adhesion value of avocado oil nano-emulgel preparations during the storage cycle, so it can be said that NE1 and NE2 are not stable during 28 days of storage. The adhesion value started changing on day 21. The adhesion values of NE1 and NE2 have decreased during storage due to a reduction in viscosity. However, the adhesion values remain adequate for effective topical preparation, not exceeding 4 seconds (Numberi, 2020).

**Table 5.** The result of the adhesion test of avocado oil nano-emulgel with carbopol 980 as a gel base. Description: *NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980, Data displayed  $n = 3 \pm SD$ .*

| Day            | Adhesion (minute) |            |            |
|----------------|-------------------|------------|------------|
|                | NE1               | NE2        | NE3        |
| Before storage | 5.43±0.07         | 15.20±0.08 | 30.34±0.07 |
| 7              | 5.40±0.11         | 15.32±0.14 | 30.27±0.14 |
| 14             | 5.81±0.09         | 15.34±0.09 | 30.25±0.08 |
| 21             | 4.76±0.03         | 14.74±0.06 | 30.27±0.15 |
| 28             | 4.22±0.18         | 14.36±0.26 | 30.31±0.20 |
| p value        | 0.000             | 0.000      | 0.541      |

The results of the spreadability test of avocado oil nano-emulgel preparations for NE1, NE2 and NE3 can be seen in Table 6. The spreadability of the skin preparation is crucial to evaluate as it pertains to the user's ease of application. The broader the active material, the more effectively it will be dispersed (Numberi, 2020). The avocado oil nano-emulgel spreadability test results showed that NE1 can spread more widely than NE2 and NE3. The results showed that the higher the concentration of the gelling agent, the smaller the spreadability value obtained. The results are due to the interconnection between spreadability and viscosity. As the viscosity of the preparation increases, its spreadability decreases; conversely, a decrease in viscosity results in enhanced spreadability.

Based on the results of statistical analysis, the value of the spreadability of avocado oil nano-emulgel shows significant results ( $p > 0.05$ ) in NE3, which means that there was no significant difference in the value of the spreadability of avocado oil nano-emulgel preparations during the storage cycle, so it can be said that NE3 is stable for 28 days of storage. Whereas in NE1 and NE2, the significant results ( $p < 0.05$ ) mean a significant difference in the value of the spreadability of avocado oil nano-emulgel preparations during the storage cycle. The

spreadability values of NE1 and NE2 increased during storage, influenced by viscosity and reduced adhesion. However, spreadability should not be considered absolute data, as no literature provides an exact ideal value (Numberi, 2020).

**Table 6.** The result of the spreadability test of avocado oil nano-emulgel with Carbopol 980 as a gel base. *Description:* NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980, Data displayed n = 3 ±SD.

| Day            | Spreadability (cm) |           |           |
|----------------|--------------------|-----------|-----------|
|                | NE1                | NE2       | NE3       |
| Before storage | 5.14±0.10          | 3.72±0.02 | 3.54±0.02 |
| 7              | 5.19±0.10          | 3.75±0.04 | 3.57±0.05 |
| 14             | 5.17±0.13          | 3.85±0.02 | 3.57±0.05 |
| 21             | 5.45±0.02          | 4.00±0.02 | 3.53±0.02 |
| 28             | 5.38±0.02          | 3.97±0.01 | 3.61±0.03 |
| p value        | 0.025              | 0.012     | 0.146     |

The results of the SPF value test for avocado oil nano-emulgel preparations for NE1, NE2 and NE3 can be seen in Table 7. The results of the SPF value showed that all of the formulas were categorized as having maximum protection. This aligns with previous research conducted by Shabrina et al. (2024) on nanoemulsion and nanoemulgel preparations using 5% avocado oil, which resulted in the maximum protection category (Shabrina, 2024). The SPF values measured over a 28-day storage period in NE1 and NE2 exhibited fluctuations, while NE3 remained stable. Several factors cause SPF value, including the type of sunscreen solvent, concentration and combination of sunscreens, type of emulsion, and the interaction and effect of other formulation components, including esters, emollients, and emulsifiers, which are some of the elements that affect the estimated SPF value. Increased or decreased absorption of UV radiation may be due to some of these variables (Mbanga et al., 2014).

**Table 7.** The result of the SPF value of avocado oil nano-emulgel with carbopol 980 as a gel base. *Description:* NE1 = nano-emulgel with 0,50% of Carbopol 980, NE2 = nano-emulgel with 1,00% of Carbopol 980, NE3 = nano-emulgel with 1,50% of Carbopol 980, Data displayed n = 3 ±SD.

| Day            | SPF Value |            |            |
|----------------|-----------|------------|------------|
|                | NE1       | NE2        | NE3        |
| Before storage | 9.02±0.81 | 11.93±0.38 | 22.38±0.24 |
| 7              | 8.95±0.43 | 12.01±0.36 | 22.41±0.21 |
| 14             | 9.65±0.09 | 11.96±0.08 | 22.34±0.32 |
| 21             | 9.71±0.27 | 12.01±0.23 | 22.42±0.27 |
| 28             | 9.80±0.18 | 11.98±0.02 | 22.37±0.23 |
| p value        | 0.468     | 0.255      | 0.107      |

Based on the results of statistical analysis, the SPF value of avocado oil nano-emulgel preparations showed significant results ( $p > 0.05$ ) in all formulas, which means that there is no

significant difference in the SPF value of avocado oil nano-emulgel preparations during the storage cycle.

Nano-emulgel with Carbopol 980 base obtained physically stable results. The results obtained by nano-emulgel are by the previously determined TPP (target product profile) (R. S. Oliveira et al., 2022). Carbopol 980 was the best at modifying the rheological properties and viscosity of nanoscale emulsions designed for topical applications (Kumara et al., 2015). Carbopol 980 demonstrated favourable test outcomes, indicating its potential as an effective carrier for topical formulations (Md et al., 2020). This research is in line with the previous result that using 1.5% w/v Carbopol 980 as a gelling agent resulted in rheologically stable results and was acceptable for topical application (Shukla et al., 2019; Verma et al., 2023). Increasing the concentration of Carbopol 980 as a gelling agent can improve the physical properties of the preparation (Kelessidis et al., 2011). Carbopol 980, as a gelling agent with a concentration of 1.5%, has good stability and did not show significant physical/chemical changes in nano-emulgel preparations (Thombre et al., 2022)(Wani et al., 2015).

#### 4. CONCLUSION

Based on the result above, it can be concluded that avocado oil in nano-emulgel preparation with 1,5% of Carbopol 980 was stable during 28 days of storage at  $30\pm 2^{\circ}\text{C}$  and RH of  $65\pm 5\%$ .

#### ACKNOWLEDGEMENT

The author would like to thank Yayasan Wahid Hasyim, Semarang, for funding this research through DIPA Unwahas 2023 in the Interdisciplinary Research scheme.

#### CONFLICT OF INTEREST

All authors declared that there was no conflict of interest.

#### REFERENCES

- Abdullah, N. I. W., Samsudin, M. N., & Othman, S. F. C. (2023). Assessing the Stability of Peppermint Oil Encapsulated in Hydrogel Beads. *Journal of Tropical Life Science*, 13(1), 51–60. <https://doi.org/10.11594/jtls.13.01.06>
- Al-Awady, M. J., Fauchet, A., Greenway, G. M., & Paunov, V. N. (2017). Enhanced antimicrobial effect of berberine in nanogel carriers with cationic surface functionality. *J. Mater. Chem. B*, 5(38), 7885–7897. <https://doi.org/10.1039/C7TB02262J>
- Alhasso, B., Ghorri, M. U., & Conway, B. R. (2023). Development of a Nanoemulgel for the Topical Application of Mupirocin effectively releases Mupirocin. *Pharmaceutics*, 15, 1–26.
- Allen, L. V. (1998). *The Art and Terminology of Pharmaceutical Compounding*. American Pharmaceutical Association, Washington DC.
- Artanti, A. N., Prihapsara, F., Mas'ud, N., & Ermawati, D. E. (2021). Optimization of the Proportion of Surfactant, Co-Surfactant, and Candlenut Oil for Self-Nanoemulsifying Drug Delivery System (SNEDDS) of Secang Heartwood (*Caesalpinia sappan* L.) Methanolic Extract. *ALCHEMY Jurnal Penelitian Kimia*, 17(1), 124. <https://doi.org/10.20961/alchemistry.17.1.39054.124-131>
- Chandra, D., & Rahman. (2022). Uji Fisikokimia Sediaan Emulgel Ekstrak Etanol Goji Berry

- (*Lycium barbarum* L.). *Medfarm: Jurnal Farmasi Dan Kesehatan*, 11(2), 219–228.
- Dantas, M. G. B., Reis, S. A. G. B., Damasceno, C. M. D., Rolim, L. A., Rolim-Neto, P. J., Carvalho, F. O., Quintans-Junior, L. J., & Da Silva Almeida, J. R. G. (2016). Development and Evaluation of Stability of a Gel Formulation Containing the Monoterpene Borneol. *Scientific World Journal*, 2016, 10–13. <https://doi.org/10.1155/2016/7394685>
- De Oliveira, A. P., Franco, E. D. S., Rodrigues Barreto, R., Cordeiro, D. P., De Melo, R. G., De Aquino, C. M. F., E Silva, A. A. R., De Medeiros, P. L., Da Silva, T. G., Góes, A. J. D. S., & Maia, M. B. D. S. (2013). Effect of semisolid formulation of persea americana mill (Avocado) oil on wound healing in rats. *Evidence-Based Complementary and Alternative Medicine*, 2013. <https://doi.org/10.1155/2013/472382>
- Depkes RI. (1995). *Farmakope Indonesia keempat* (Edisi IV). Departemen Kesehatan Republik Indonesia, Jakarta.
- Dewi, R. H. T. M., Sholihah, N., Nofitasari, R., Adhityasmara, D., & Shabrina, A. (2024). The Potential of Avocado Oil for Topical Use: A Narrative Review. *Jurnal Ilmu Farmasi Dan Farmasi Klinik*, 21(1), 106. <https://doi.org/10.31942/jiffk.v21i1.11218>
- Ebad Sichani, M. R., Farid, M., & Khorasgani, E. M. (2021). Histomorphological Examination of Skin Wound Healing Under the Effect of Avocado Oil in Wistar Rats. *Acta Veterinaria Eurasia*, 47(3), 121–128. <https://doi.org/10.5152/actavet.2021.20096>
- Eid, A. M., Elmarzugi, N. A., & El-Enshasy, H. A. (2013). Development of Avocado Oil Nanoemulsion Hydrogel Using Sucrose Ester Stearate. *Journal of Applied Pharmaceutical Science*, 3(12), 145–147. <https://doi.org/10.7324/JAPS.2013.31226>
- FDA. (2013). ASEAN guideline on stability study of drug product. *Asean Guideline On Stability Study Of Drug Product (RI) Revision, May*, 1–40.
- Ghani, H., Rahman, R. K., Liu, K., & Cubelli, S. (2021). An Investigation of Makeup Ingredients and Their Effects on Acne Cosmetics with Dermatologic Practice Recommendations. *SKIN: Journal of Cutaneous Medicine*, 5(5), 474–481. <https://doi.org/10.25251/skin.5.5.4>
- Hardenia, A., Jayronia, S., & Jain, S. (2014). Emulgel : An Emergent Tool in Topical Drug Delivery. *International Journal of Pharmaceutical Sciences and Research*, 5(5), 1653–1660. [https://doi.org/10.13040/IJPSR.0975-8232.5\(5\).1653-60](https://doi.org/10.13040/IJPSR.0975-8232.5(5).1653-60)
- Hermanto, S., Muawanah, A., & Wardhani, P. (2010). Analisis Tingkat Kerusakan Lemak Nabati dan Lemak Hewani Akibat Proses Pemanasan. *Jurnal Kimia VALENSI*, 1(6), 262–268. <https://doi.org/10.15408/jkv.v1i6.237>
- Ikhtiyarini, T. A., & Sari, A. K. (2022). Efektivitas Penggunaan Basis Gel pada Sediaan Emulgel Effectiveness of Basic Use for Emulgel Preparations. *Camellia*, 1(1), 19–25.
- Islam, M. T., Rodríguez-Hornedo, N., Ciotti, S., & Ackermann, C. (2004). Rheological characterization of topical carbomer gels neutralized to different pH. *Pharmaceutical research*, 21(7), 1192–1199. <https://doi.org/10.1023/b:pham.0000033006.11619.07>
- Jo, M., Chang, M. J., Goh, K. K. T., Ban, C., & Choi, Y. J. (2021). Emulsion-filled gels' gels' rheology, microstructure, and storage stability are stabilized solely by maize starch modified with octenyl succinylation and pregelatinization. *Foods*, 10(4). <https://doi.org/10.3390/foods10040837>
- Kelessidis, V. C., Poulakakis, E., & Chatzistamou, V. (2011). Use Carbopol 980 and carboxymethyl cellulose polymers as rheology modifiers of sodium-bentonite water dispersions. *Applied Clay Science*, 54(1), 63–69. <https://doi.org/10.1016/j.clay.2011.07.013>
- Kumara, P., Prakash, N. K. S., Lokesh, & Manral, D. K. (2015). Viscoelastic Properties and Rheological Characterization of Carbomers. *Int. J. Latest Res. Eng. Technol.*, 1(6), 2454–5031.

- Kuncari, E. S., Iskandarsyah, & Praptiwi. (2014). Evaluasi, Uji stabilitas fisik dan sineresis sediaan gel yang mengandung minoksidil, apigenin dan perasan herba seledri (*Apium graveolens L.*) Evaluation, Physical stability test and syneresis of gel containing minoxidil, apigenin and celery (*Apium graveo.* *Bul. Penelit. Kesehat.*, 42(4), 213–222.
- Li, Y., Liu, Y., Deng, D., Liang, J., Chen, W., Chen, X., & Li, J. (2019). Study on Extracting Avocado Oil from Avocado Pulp by Aqueous Extraction. *IOP Conference Series: Earth and Environmental Science*, 330(4). <https://doi.org/10.1088/1755-1315/330/4/042027>
- Mansur JS, Breder MNR, Mansur MCA, A. R. (1986). *Mansur JS, Breder MNR, Mansur MCA, Azulay RD.1986. Determination of Sun Protection Factor for Spectrophotometry. An Bras Dermatol Rio De Janeiro*, 61, 121- 4.
- Mardiyanto, Mohadi, R., Fithri, N. A., & Kurniawan, G. (2024). Optimization of Nanoemulsion Formula Containing Erythromycin with VCO and Varying Concentrations of Tween-80 and PEG-400. *Science and Technology Indonesia*, 9(3), 697–709. <https://doi.org/10.26554/sti.2024.9.3.697-709>
- Mbanga, L., Mpiana, P. T., Bokolo, K., Mvingu, K., Ngoy, B., Muwara, K., & Mulenga, M. (2014). Sun Protection Factor (SPF) Determination of Cosmetic Formulations Made in Kinshasa (DR Congo) by in-vitro Method Using UV-VIS Spektrophotometer. *Journal of Physical and Chemical Sciences*, 2(1), 1–5.
- Md, S., Alhakamy, N. A., Aldawsari, H. M., Kotta, S., Ahmad, J., Akhter, S., Alam, M. S., Khan, M. A., Awan, Z., & Sivakumar, P. M. (2020). Improved analgesic and anti-inflammatory effect of diclofenac sodium by topical nanoemulgel: Formulation development—in vitro and in vivo studies. *Journal of Chemistry*, 2020. <https://doi.org/10.1155/2020/4071818>
- Nabillah, S., Noval, N., & Hidayah, N. (2022). FORMULASI DAN EVALUASI NANO HIDROGEL EKSTRAK DAUN SERUNAI (*Chromolaena odorata L.*) DENGAN VARIASI KONSENTRASI POLIMER CARBOPOL 980. *Jurnal Ilmiah Ibnu Sina (JIIS): Ilmu Farmasi Dan Kesehatan*, 7(2), 340–349. <https://doi.org/10.36387/jiis.v7i2.995>
- Numberi, A. M. (2020). Uji Stabilitas Fisik Sediaan Masker Gel dari Ekstrak Alga Merah (*Poryphyra* sp). *Majalah Farmasetika*, 5(1), 1–17. <https://doi.org/10.24198/mfarmasetika.v5i1.24066>
- Oliveira, R. S., da Silva, D. F., Mota, S., Garrido, J., Garrido, E. M., Lobo, J. M. S., & Almeida, I. F. (2022). Design of an Emulgel for Psoriasis Focused on Patient Preferences. *Applied Sciences (Switzerland)*, 12(7). <https://doi.org/10.3390/app12073260>
- Patricia, P., & Yuliani, S. H. (2015). Pembuatan Dan Uji Aktivitas Sediaan Unguenta Scarless Wound Dengan Ekstrak Binahong Dan Zat Aktif Aspirin. *Jurnal Farmasi Sains Dan Komunitas*, 12(2), 54–60.
- Priani, S. E., Abdilla, S. A., & Suparnan, A. (2020). Pengembangan Sediaan Mikroemulsi Gel Antijerawat Mengandung Minyak Kulit Batang Kayu Manis (*Cinnamomum burmanni Nees ex Bl.*). *Jurnal Ilmiah Farmasi Farmasyifa*, 3(1), 9–17. <https://doi.org/10.29313/jiff.v3i1.5464>
- Rao, M. R., Deshpande, S., & Deshpande, P. (2023). Dapsone-Loaded Mixed Micellar Gel for Treatment OF Acne Vulgaris. *AAPS PharmSciTech*, 24(5), 109. <https://doi.org/10.1208/s12249-023-02564-1>
- Rismawati, D., Aji, N., & Herdiana, I. (2020). Pengaruh Butylated Hydroxyanisole terhadap Stabilitas dan Karakteristik Emulgel Kombinasi Ekstrak Jahe Merah dan Minyak Peppermint. *Jurnal Ilmiah Kefarmasian*, 1(2), 35–41.
- Scomorosenco, C., Teodorescu, M., Raducan, A., Stan, M., Voicu, S. N., Trica, B., Ninciuleanu, C. M., Nistor, C. L., Mihaescu, C. I., Petcu, C., & Cinteza, L. O. (2021). Novel gel microemulsion as topical drug delivery system for curcumin in

- dermatocosmetics. *Pharmaceutics*, 13(4).  
<https://doi.org/10.3390/pharmaceutics13040505>
- Shabrina, A. (2024). Physical Stability and Effectivity Comparison of Nanoemulsion and Nano-emulgel of Avocado Oil with Carbopol 940 Variation. *Indonesian Journal of Pharmaceutical Science and Technology*, 6(1), 8–17.
- Shabrina, A., Firdausi, Z. M., Poerba, A. T., Anisa, D., & Heroweti, J. (2024). Sunscreen effectivity and physical characterization of avocado oil in nanoemulsion using isopropyl myristate variations. *Pharmaciana*, 14(1), 69–79.  
<https://doi.org/10.12928/pharmaciana.v14i1.28214>
- Shabrina, A., Heroweti, J., Yumni, G. G., Poerba, A. T., & Diana, A. (2024). Physical Stability and Effectivity Comparison of Nanoemulsion and Nano- emulgel of Avocado Oil with Carbopol 940 Variation. *Indonesia Journal of Pharmaceutical Sciences and Technology*, 6(1), 6–17.
- Shelke, O., & Kulkarni, A. (2019). Formulation, development and evaluation of nifedipine emulgel for treatment of anal fissures using polymeric emulsifiers. *Indian Journal of Pharmaceutical Education and Research*, 53(2), s74–s81.  
<https://doi.org/10.5530/ijper.53.2s.51>
- Shukla, K. V., Sharma, A., & Yadav, M. (2019). Formulation Development and Evaluation of Ethosomal Gel of Acyclovir for the Treatment of Herpes Zoster. *Journal of Drug Delivery and Therapeutics*, 9(4-A), 664–668.  
<http://jddtonline.info/index.php/jddt/article/view/3548>
- Sreevidya, V. S. (2019). An Overview on Ebola. *Global Dermatology*, 2(1), 92–97.  
<https://doi.org/10.15761/god.1000122>
- Suhesti, T. S., Rohman, M. M. H., & Sunarto, S. (2022). Formulation of Gel Hand Sanitizer of Nagasari Leaf Extract (*Mesua ferrea* L.). *Indonesian Journal of Pharmaceutical Science and Technology*, 1(1), 31. <https://doi.org/10.24198/ijpst.v1i1.36465>
- Suradnyana, I. G. M., Juliadi, D., & Suen, N. M. D. S. (2023). Formulasi serta Uji Aktivitas Antioksidan dan Tabir Surya Krim Ekstrak Aseton Biji Buah Alpukat. *Jurnal Ilmiah Medicamento*, 9(1), 42–51. <https://doi.org/10.36733/medicamento.v9i1.5504>
- Suryani, Sahumena, M. H., Mabilla, S. Y., Ningsih, S. R., Adjeng, A. N. T., Aswan, M., Ruslin, Yamin, & Nisa, M. (2020). Preparation and Evaluation of Physical Characteristics of Vitamin E Nanoemulsion Using Virgin Coconut Oil (VCO) and Olive Oil as Oil Phase with Variation Concentration of Tween 80 Surfactant. *Research Journal of Pharmacy and Technology*, 13(7), 3232–3236. <https://doi.org/10.5958/0974-360X.2020.00572.7>
- Thombre, N. A., Niphade, P. S., D. Ahire, E., & J. Kshirsagar, S. (2022). Formulation Development and Evaluation of Microemulsion Based Lornoxicam Gel. *Biosciences Biotechnology Research Asia*, 19(1), 69–80. <https://doi.org/10.13005/bbra/2968>
- Verma, P., Dutt, R., & Anwar, S. (2023). Formulation and development of novel probiotic loaded gel for the treatment of caffeine induced anxiety. *Journal of Applied Pharmaceutical Science*, 13(6), 121–127. <https://doi.org/10.7324/JAPS.2023.100861>
- Voigt, R. (1984). *Buku Ajar Teknologi Farmasi*. diterjemahkan oleh Soewandi, S. N., UGM Press, Yogyakarta.
- Wani, R. R., Patil, M. P., Dhurjad, P., Chaudhari, C. A., & Kshirsagar, S. J. (2015). Microemulsion Based Gel: A Novel Approach In Delivery of Hydrophobic Drug. *International Journal for Pharmaceutical Research Scholars*, 4(2), 671–677.
- Widyastuti, A. I., & Saryanti, D. (2023). Formulasi dan Evaluasi Sediaan Nanoemulsi Ekstrak Umbi Bawang Putih (*Allium sativum* L.). *Jurnal Sains Dan Kesehatan*, 5(2), 178–185.  
<https://doi.org/10.25026/jsk.v5i2.1677>
- Yuliandri, M., Saádah, H., & Warnida, H. (2021). Pengaruh Konsentrasi Carbopol 940 Sebagai Gelling Agent Terhadap Sifat Fisik Dan Stabilitas Gel Hand. *Library.Usd.Ac.Id*, 117–

124. [http://www.library.usd.ac.id/Data PDF/F. Farmasi/Farmasi/108114120\\_full.pdf](http://www.library.usd.ac.id/Data%20PDF/F.%20Farmasi/Farmasi/108114120_full.pdf)  
Zalivskaya, A., Fadeeva, D., Shestopalova, N., Avtina, N., Radyukova, V., & Ivanova, V.  
(2021). Comparative characteristics of gel bases for semisolid dosage forms. *BIO Web of  
Conferences*, 40, 03008. <https://doi.org/10.1051/bioconf/20214003008>