

## Mekanika: Majalah Ilmiah Mekanika

---

### Nanofiber Semiconductor Experiment with Distance Variation Electrospinning Method to Improve the Efficiency of the Dssc

Denny Widhiyanuriyawan<sup>1</sup>, Zainal Arifin<sup>2,\*</sup>, Syamsul Hadi<sup>2</sup>, Muhammad Rijalul Fadli<sup>2</sup>

1 Department of Mechanical Engineering, Universitas Brawijaya, Malang, Indonesia

2 Mechanical Engineering Department, Universitas Sebelas Maret, Surakarta, Indonesia

\*Corresponding Author's: zainal\_arifin@staff.uns.ac.id

#### Keywords:

DSSC, electrospinning,  
rotating collector, distance

**Abstract.** Dye-Sensitized Solar Cell (DSSC) is a type of solar cell that uses dyes to transfer sunlight to electrical energy. DSSC construction uses a layered system (sandwich) that consists of a working electrode and an opposing electrode, both of which are placed on conducting glass and electrolytes to allow electron cycling. DSSC has a high price, so increasing efficiency is needed so that these solar cells can be used more widely. This research aims to determine the effect of the distance between the tip and the rotating collector in an effort to increase the efficiency of Dye-Sensitized Solar Cell (DSSC) and examine its impact on the morphology of the ZnO nanofiber. This experiment is carried out by varying the distance between the tip to the rotating collector, which are 4 cm, 6 cm, and 8 cm. The results of this research indicates that at a distance of 8 cm it produces a small, uniform and regular ZnO nanofiber structure with Voc, Jsc, FF, and DSSC efficiency values of 0.559 V, 9.809 mA / cm<sup>2</sup>, 43.3% and 2.3%. In addition, at a distance of 8 cm it also produces the highest DSSC electrical efficiency from the other distances due to the absorbance of the dye and high electron excitation.

### 1 Introduction

Energy is the main source of life in the world. The use of energy in society still depends on non-renewable fossil fuels such as petroleum, coal, and natural gas. This fossil fuel is not only limited in use, but also can cause environmental pollution. To overcome this problem, another alternative fuel is needed, therefore researchers focused on clean and renewable energy sources, namely using solar energy. Solar energy is a source of energy that produces heat and radiation. Solar cells are a tool that can convert solar radiation into electrical energy through a photovoltaic process [1], [2].

Solar cells have been developed from generation to generation with different characterization and different components, namely silicon-based solar cells, thin film-based solar cells (thin film) and DSSC.

---

<https://dx.doi.org/10.20961/mekanika.v21i1.51479>

Received 27 May 2021; received in revised version 20 February 2022; Accepted 21 March 2022  
Available Online 31 March 2022

2579-3144

© 2022 Mekanika: Majalah Ilmiah Mekanika. All right reserved

Widhiyanuriyawan et al.

Silicon-based solar cells are solar cells made of silicon and have a very high efficiency. The disadvantage of this solar cell is that it is expensive to produce. Thin film based solar cells are a development of silicon solar cells which have lower efficiency than silicon solar cells but are more economical. The price is cheaper than silicon solar cells [3], [4]. The DSSC (Dye-Sensitized Solar Cell) solar cell was first discovered by Michael Gratzel in 1991. The results of Gratzel's research show that DSSC has a relatively cheap price compared to the previous generation, simple fabrication and environmentally friendly materials used [5]. DSSC consists

of 5 layers, namely FTO glass, semiconductor, dye, electrolyte and counter electrode [6].

The efficiency of the DSSC depends on the semiconductor that must have high electron mobility and a surface area to absorb the dye. Currently, DSSC has an efficiency of 15% [7]. Semiconductor materials that are often used in DSSC are  $\text{TiO}_2$  and  $\text{ZnO}$ . Both have their own advantages and disadvantages, including the advantages of  $\text{ZnO}$ , namely having a wide band gap of 3.37 eV [8] and the high electron mobility of  $\text{TiO}_2$  [9] while the drawback is the level of chemical stability which is quite low.  $\text{TiO}_2$  has advantages, namely high color adsorption ability, high chemical stability but the disadvantage of  $\text{TiO}_2$  is that it has a low band gap of 3.2 eV [8]. To get optimal performance, the Double Layer method is used. This method is used to form a DSSC anode by using several semiconductor layers in order to form a DSSC anode in order to have good performance.

The electrospinning method with a rotating collector is a method of making nanofiber fibers that has an easy working principle and can maintain the uniformity of the nanofiber produced. In principle, electrospinning utilizes the electrostatic force that arises from charged particles due to a high voltage between the tip of the tip and the rotating collector [10].

Photoanode of DSSC made of nanomaterial with different morphologies are nanofibers, nanowires, nanorods, nanobelts, nanotubes, nano spiral, nano rings [11], and nanoparticle [12]. Nanofiber has the advantage that the form of nanofiber morphology can provide direct electron flow from photogeneration to the conductive substrate and the branching structure makes the morphology of the nanofiber has a high surface area. Nanofiber structure that can stick to the substrate and the dye will directly facilitate the mobility of electrons that have been excited.

The direct deposition method is a coating technique on nanomaterials with an electrospinning process in which the precursor solution is sprayed directly onto the FTO glass. The benefit of this method is that the  $\text{ZnO}$  coating process on the DSSC assembly will be shorter and reduce nanofiber damage. Meanwhile, the attachment process to nanomaterials such as doctor blade, slip casting and spin coating uses a similar technique by coating the nanomaterial from a paste form into a thin layer on FTO glass. The process before coating the nanomaterial-paste is by making a solution first, then the solution is converted into a nanomaterial that has been sintered [13]. This method still has some disadvantages such as a longer procedure and is capable of damaging the nanofibers.

In this study, the DSSC photoanode manufacturing process will be examined using distance variations in the electrospinning process with the direct deposition method on a rotating collector and a method of coating nanomaterials using  $\text{ZnO}$  material with an electrospinning process where the results of spraying  $\text{ZnO}$  solution will be captured directly by the FTO which has been coated with  $\text{TiO}_2$  nanoparticles. and glued to the rotating collector. So, the direct deposition method using electrospinning with a rotating collector will shorten the DSSC fabrication process and hopefully reduce the damage to the nanofiber produced and produce good performance.


## 2 Experimental Methods

### 2.1 preparation of photoanode

This research uses semiconductor types of  $\text{ZnO}$  nanofiber and  $\text{TiO}_2$  nanoparticles. To obtain the morphology of the nanofiber, an electrospinning process was carried out with a rotating collector. So that semiconductors need to be added to precursor solutions which are polymers with good electrical conductivity. Preparation of precursors using 10 grams of PVA (merck, MW = 72,000) mixed with 10 ml

Widhiyanuriyawan et al.

of distilled water ( $H_2O$ ). To produce a homogenized solution, the stirring process was carried out for 4 hours at a solution temperature of  $70\text{ }^{\circ}C$ . The  $Zn (Ac)_2$  solution was synthesized using 2 grams of zinc acetate dihydrate ( $(CH_3COO)_2Zn \cdot 2H_2O$ , Merck) and 8 ml of  $H_2O$ , after which the homogeneity process was carried out by stirring for 1 hour keeping the solution at  $70\text{ }^{\circ}C$ . The homogenization process between the PVA and  $Zn (Ac)_2$  solution was carried out in a ratio of 4: 1 wt% at  $70\text{ }^{\circ}C$  for 8 hours. Furthermore, the  $Zn (Ac)_2 / PVA$  solution was left to stand at room temperature for 24 hours to remove the formed foam [14], [15]. So that a  $Zn (Ac)_2 / PVA$  solution is produced which is used to produce ZnO nanofiber fibers using an electrospinning machine with a rotating collector as shown in Figure 1.

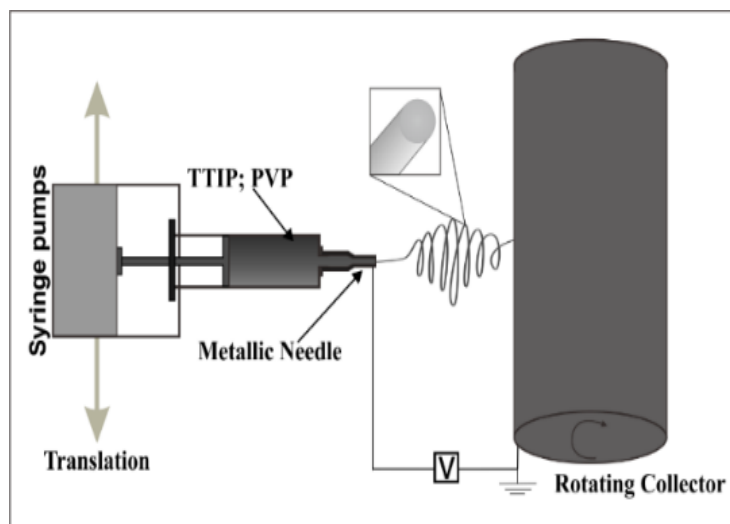

**FIGURE 1.** Schematic illustration of electrospinning with rotating collector [16]

The solution that has been synthesized is then put into 1 ml of the electrospinning solution pump injection. The main part of the electrospinning device consists of a high-voltage DC source, a spinneret tube, a small diameter needle with an inner diameter of  $200\text{ }\mu m$  which is connected to the positive 15 kV high voltage terminal to the plate on the rotating collector made of metal to which FTO glass has been deposited with  $TiO_2$  nanoparticles and connected to the negative terminal using the direct deposition method (Figure 1). The flow rate of the solution through the needle is  $4\text{ }\mu L / \text{minute}$  because it can produce more uniform nanofiber fibers. The tip distance to the rotating collector uses a variation of 4,6,8 cm. the rotating speed at the collector is 45 rpm. The solution then attaches itself to the surface of the collector plate in the form of pulling strands called green fibers. The green fibers were then centered at a temperature of about  $500^{\circ}C$  with 1 hour holding to remove organic matter and formation of ZnO crystals [17]. The result of nanofiber deposition on FTO coated with  $TiO_2$  nanoparticles can be used as a double layer photoanode.

## 2.2 DSSC Fabrication and Testing Process

After the sintering process is carried out, the FTO is left to cool then soaked in sintizer-N719 dye ( $[RuL_2 (NCS)_2] : 2TBA$  (L = 2,2'-bipyridyl-4,4'-dicarboxylic acid; TBA = tetra- n-butylammonium)) from Dyesol for 1 day. The DSSC fabrication process is carried out by combining the FTO with a counter electrode, including semiconductors and dye. Then the electrolyte solution is placed between the FTO and the counter electrode using the injection method. The electrolyte used in this study was Iodide ( $I_3^-$ ) EL-HPE from Dyesol. In general, the performance of the DSSC can be characterized by several electrical parameters, including the photocurrent-voltage curve (JV curve), open-circuit photovoltage ( $V_{OC}$ ), short-circuit photocurrent density ( $J_{SC}$ ), fill factor (FF), and efficiency. ( $\eta$ ). The measurement is carried out by shining the DSSC at the measured intensity (generally  $100\text{ mW} / \text{cm}^2$ ) and given a variation of the electric load from zero to infinity, then the voltage and current are measured every time [18]. The results of the measurements are in the form of voltage and current values which are plotted in a graph as in Figure 2.

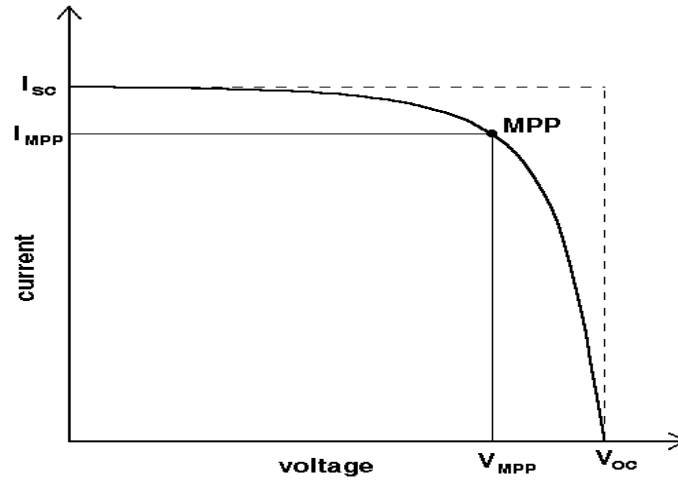


FIGURE 2. Current-voltage curve (I-V curve) on DSSC [18]

From the voltage current curve (Figure 2.5) it can be seen that the fill factor (FF) value, that the fill factor is a parameter that determines the efficiency of the DSSC. Graphically, the fill factor is the ratio between the maximum power (PMPP) to the multiplication of short-circuit current ( $I_{SC}$ ) and open circuit voltage ( $V_{OC}$ ). To find out the fill factor (FF) value, you can use the following equation [18].

$$FF = \frac{V_{MPP} \times I_{MPP}}{I_{SC} \times V_{OC}} \quad (1)$$


The efficiency of the DSSC solar cell is the ratio between the maximum power (PMPP) to the power emitted by light in the active region of the solar cell ( $P_{light}$ ). Which where ( $P_{light}$ ) is the multiplication of sunlight intensity ( $I_{rad}$ ) to the active area of the solar cell ( $A$ ) [19].

$$\eta = \frac{P_{MPP}}{P_{light}} = \frac{P_{MPP}}{I \times A} = \frac{I_{SC} \times V_{OC} \times FF}{I \times A} \quad (2)$$

### 3. Result and Discussion

#### 3.1 Uji Morfologi Nanofiber DSSC


Figure 3 shows the results of the SEM ZnO nanofiber test by using the shorter tip distance to the rotating collector, which will result in an irregular morphology of the nanofiber, has a large diameter and has branches like dendrites on nerves. This situation occurs due to poor solvent evaporation which causes irregular beading and build-up of nanofiber, as shown in Figure 3 (a). The shorter the tip distance to the rotating collector, the less solvent evaporation process, so that the solvent adhering to the FTO glass is less than perfect. This is consistent with previous research, which states that the distance between the tip and the rotating collector has sufficient evaporation time for the nanofiber to fully adhere to the FTO glass, resulting in a thinner and uniform nanofiber. Meanwhile, with the decreasing distance between the tip and the rotating collector, the resulting nanofiber is irregular, the nanofiber becomes branched, and there are lumps in the resulting nanofiber.

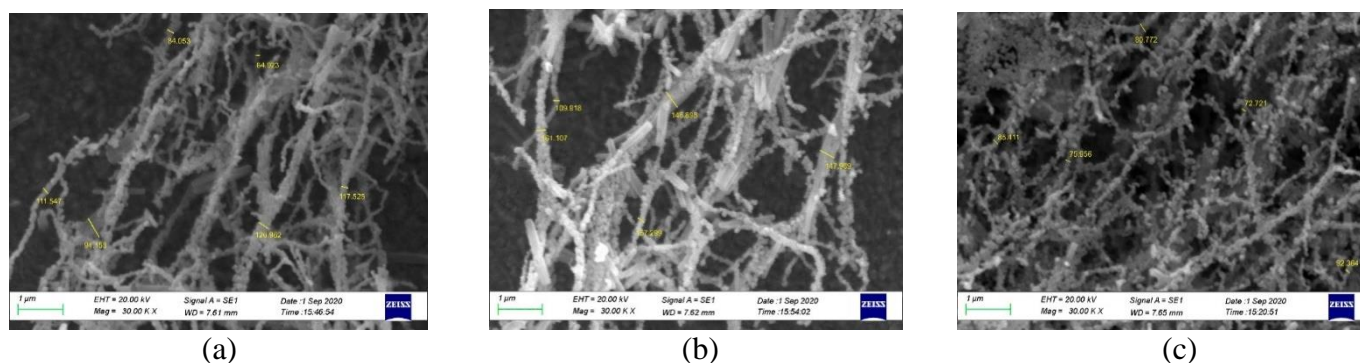

**FIGURE 3.** SEM test results for ZnO nanofiber with variations in tip distance to rotating collector, (a) 4 cm; (b) 6 cm; and (c) 8 cm with a flow rate of 4  $\mu\text{L}$  / minute

### 3.2 DSSC performance

The voltage current curve shows the performance of Dye Sensitized Solar Cells (DSSC) solar cells at a tip to collector rotating distance of 4.6, and 8 cm. It is known that the voltage current curve on the DSSC is shown in Figure 4. Some of the DSSC performance parameters include short-circuit photocurrent density ( $J_{sc}$ ) of 5 mA / cm, open-circuit photovoltage ( $V_{oc}$ ) of 0.658 V, fill factor (FF) of 0.29 % and efficiency of 0.98% for the tip distance to the rotating collector of 8 cm which can produce the highest current. However, the efficiency values at the tip to collector rotating distance of 4 cm and 6 cm are shown in Table 2. The results of this study indicate that the  $J_{sc}$  value affects the resulting efficiency value. The more the  $J_{sc}$  value increases, the DSSC efficiency value will also increase.

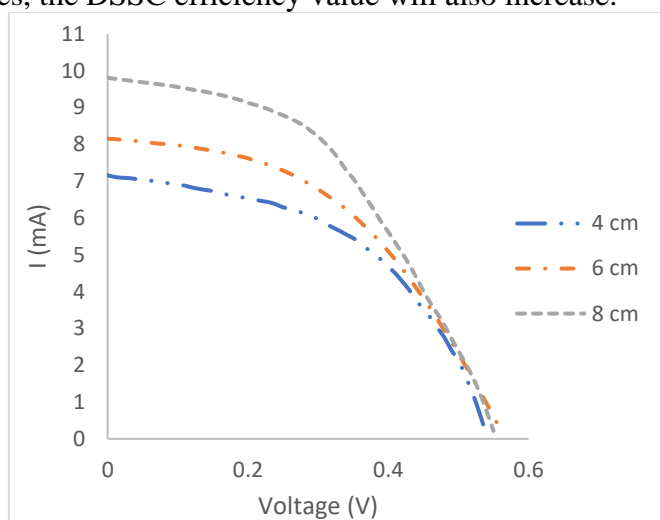

**FIGURE 4.** Current-voltage curve ( $I$ - $V$  curve) on DSSC

**TABLE 1.** The performance of DSSC

Distance (cm)	$V_{oc}$ (V)	$J_{SC}$ (mA/cm <sup>2</sup> )	FF (%)	$\eta$ (%)
4	0.544	7.1	48	1.91
6	0.566	8.1	45.8	2.11
8	0.559	9.8	43.3	2.37

#### 4. Conclusion

The ZnO nanofiber fabrication process in the process of making photoanodes with nanofiber fibers in DSSC was carried out using an electrospinning machine with the use of variations in the distance between the tip to the rotating collector in the electrospinning process using the direct deposition method. The addition of distance in the electrospinning process will produce nanofiber fibers that have a small and uniform diameter and size so that it can improve the performance of DSSC because the distribution of electrons becomes more even. Vice versa, the larger the size and diameter of the resulting nanofiber fibres, the lower the performance of the DSSC. DSSC performance is also influenced by the value of  $J_{sc}$ , the higher the value of  $J_{sc}$ , the higher the efficiency of DSSC. In this study, the highest efficiency of the DSSC was 2.37 which was achieved at a distance of 8 cm. The  $V_{oc}$ ,  $J_{sc}$ , and FF values respectively were 0.559 V, 9.8 mA / cm<sup>2</sup>, and 43.3%.

#### 5. Acknowledgement

This work was partially supported by a PDUPT grant from the Ministry of Research, Technology, and Higher Education, the Republic of Indonesia, with contract number 112/UN27.21/HK/2020 for FY 2020.

#### References

1. W. Liu, H. Ma, and A. Walsh, "Advance in photonic crystal solar cells," *Renew. Sustain. Energy Rev.*, vol. 116, no. October, p. 109436, 2019.
2. S. D. Prasetyo, A. R. Prabowo, and Z. Arifin, "The effect of collector design in increasing PVT performance: Current state and milestone," *Mater. Today Proc.*, no. xxxx, 2022.
3. K. Petridis, "An Introduction to Organic Photo-Voltaic ( OPVs ) An Introduction to Organic Photo-Voltaic ( OPVs )," *elbysier*, no. April, 2016.
4. Z. Arifin, S. Hadi, H. N. Jati, S. D. Prasetyo, and Suyitno, "Effect of electrospinning distance to fabricate ZnO nanofiber as photoanode of dye-sensitized solar cells," *AIP Conf. Proc.*, vol. 2217, no. April, 2020.
5. T. Ponken, S. Kongsankham, S. Panya, W. Choawunklang, and P. Ardchongthong, "Effect of Titanium Dioxide (TiO<sub>2</sub>) Light Scattering Layer deposited by Spray Deposition Method at Room Temperature for Dye-sensitized Solar Cell (DSSC)," *Mater. Today Proc.*, vol. 17, pp. 1249–1258, 2019.
6. M. K. Nazeeruddin, E. Baranoff, and M. Grätzel, "Dye-sensitized solar cells: A brief overview," *Sol. Energy*, vol. 85, no. 6, pp. 1172–1178, 2011.
7. K. K. Tehare, S. T. Navale, F. J. Stadler, Z. He, and H. Yang, "Enhanced DSSCs performance of TiO<sub>2</sub> nanostructure by surface passivation layers," *Mater. Res. Bull.*, vol. 99, no. November 2017, pp. 491–495, 2018.
8. B. Boro, B. Gogoi, B. M. Rajbongshi, and A. Ramchiary, "Nano-structured TiO<sub>2</sub>/ZnO nanocomposite for dye-sensitized solar cells application: A review," *Renew. Sustain. Energy Rev.*, vol. 81, no. May 2017, pp. 2264–2270, 2018.
9. S. Suhaimi, M. M. Shahimin, Z. A. Alahmed, J. Chyský, and A. H. Reshak, "Materials for enhanced dye-sensitized solar cell performance: Electrochemical application," *Int. J. Electrochem. Sci.*, vol. 10, no. 4, pp. 2859–2871, 2015.
10. T. Wahyudi and D. Sugiyana, "PEMBUATAN SERAT NANO MENGGUNAKAN METODE ELECTROSPINNING," *Arena Tekst.*, vol. 26, no. 1, pp. 29–34, 2011.
11. S. Yun and S. Lim, "Effect of Al-doping on the structure and optical properties of electrospun zinc oxide nanofiber films," *J. Colloid Interface Sci.*, vol. 360, no. 2, pp. 430–439, 2011.
12. A. El Ruby Mohamed and S. Rohani, "Modified TiO<sub>2</sub> nanotube arrays (TNTAs): Progressive strategies towards visible light responsive photoanode, a review," *Energy Environ. Sci.*, vol. 4, no. 4, pp. 1065–1086, 2011.
13. B. D. Li and Y. Xia, "Electrospinning of Nanofibers : Reinventing the Wheel ?\*\*," no. 14, pp. 1151–1170, 2004.
14. S. Suyitno, A. Purwanto, R. L. L. G. Hidayat, I. Sholahudin, M. Yusuf, S. Huda, and Z. Arifin, "Fabrication

Widhiyanuriyawan et al.

- and characterization of zinc oxide-based electrospun nanofibers for mechanical energy harvesting,” *J. Nanotechnol. Eng. Med.*, vol. 5, no. 1, pp. 1–6, 2014.
15. Z. ARIFIN, S. HADI, S. SUYITNO, A. R. PRABOWO, and S. D. PRASETYO, “Characterization of zno nanofiber on double-layer dye-sensitized solar cells using direct deposition method,” *Period. Tche Quim.*, vol. 17, no. 36, pp. 263–277, 2020.
  16. H. N. Jati, M. Z. Khusaini, and H. Sutanto, “Application of direct deposition method for dye-sensitized solar cell manufacturing process Application of Direct Deposition Method for Dye-Sensitized Solar Cell Manufacturing Process,” *AIP Conf. Proc.*, vol. 030022, no. April, pp. 1–6, 2019.
  17. B. Sutanto, Z. Arifin, S. Hadi, and L. Muliani, “Enhancement ZnO Nanofiber as Semiconductor for Dye-Sensitized Solar Cells by Using Al Doped,” vol. 040006, 2016.
  18. L. L. Tobin, T. O’Reilly, D. Zerulla, and J. T. Sheridan, “Characterising dye-sensitised solar cells,” *Optik (Stuttg.)*, vol. 122, no. 14, pp. 1225–1230, 2011.
  19. K. Sharma, V. Sharma, and S. S. Sharma, “Dye-Sensitized Solar Cells : Fundamentals and Current Status,” *nanoscale Res. Lett.*, vol. 6, 2018.